

# RDS—21 Face-Gear Surface Durability Tests

*David G. Lewicki*

*U.S. Army Research Laboratory, Glenn Research Center, Cleveland, Ohio*

*Gregory F. Heath, Robert R. Filler, and Stephen C. Slaughter*

*The Boeing Company, Mesa, Arizona*

*Jason Fetty*

*U.S. Army Aviation Applied Technology Directorate, Ft. Eustis, Virginia*

## NASA STI Program . . . in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA Scientific and Technical Information (STI) program plays a key part in helping NASA maintain this important role.

The NASA STI Program operates under the auspices of the Agency Chief Information Officer. It collects, organizes, provides for archiving, and disseminates NASA's STI. The NASA STI program provides access to the NASA Aeronautics and Space Database and its public interface, the NASA Technical Reports Server, thus providing one of the largest collections of aeronautical and space science STI in the world. Results are published in both non-NASA channels and by NASA in the NASA STI Report Series, which includes the following report types:


- **TECHNICAL PUBLICATION.** Reports of completed research or a major significant phase of research that present the results of NASA programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA counterpart of peer-reviewed formal professional papers but has less stringent limitations on manuscript length and extent of graphic presentations.
- **TECHNICAL MEMORANDUM.** Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.
- **CONTRACTOR REPORT.** Scientific and technical findings by NASA-sponsored contractors and grantees.

- **CONFERENCE PUBLICATION.** Collected papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or cosponsored by NASA.
- **SPECIAL PUBLICATION.** Scientific, technical, or historical information from NASA programs, projects, and missions, often concerned with subjects having substantial public interest.
- **TECHNICAL TRANSLATION.** English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services also include creating custom thesauri, building customized databases, organizing and publishing research results.

For more information about the NASA STI program, see the following:

- Access the NASA STI program home page at <http://www.sti.nasa.gov>
- E-mail your question via the Internet to [help@sti.nasa.gov](mailto:help@sti.nasa.gov)
- Fax your question to the NASA STI Help Desk at 301-621-0134
- Telephone the NASA STI Help Desk at 301-621-0390
- Write to:  
NASA Center for AeroSpace Information (CASI)  
7115 Standard Drive  
Hanover, MD 21076-1320



# RDS—21 Face-Gear Surface Durability Tests

*David G. Lewicki*

*U.S. Army Research Laboratory, Glenn Research Center, Cleveland, Ohio*

*Gregory F. Heath, Robert R. Filler, and Stephen C. Slaughter*

*The Boeing Company, Mesa, Arizona*

*Jason Fetty*

*U.S. Army Aviation Applied Technology Directorate, Ft. Eustis, Virginia*

Prepared for Forum 63

sponsored by the American Helicopter Society International (AHS)

Virginia Beach, Virginia, May 1–3, 2007

National Aeronautics and  
Space Administration

Glenn Research Center  
Cleveland, Ohio 44135

*Level of Review:* This material has been technically reviewed by technical management.

Available from

NASA Center for Aerospace Information  
7115 Standard Drive  
Hanover, MD 21076-1320

National Technical Information Service  
5285 Port Royal Road  
Springfield, VA 22161

Available electronically at <http://gltrs.grc.nasa.gov>

# RDS–21 Face-Gear Surface Durability Tests

David G. Lewicki  
U.S. Army Research Laboratory  
Glenn Research Center  
Cleveland, Ohio 44135

Gregory F. Heath, Robert R. Filler, and Stephen C. Slaughter  
The Boeing Company  
Mesa, Arizona 85215

Jason Fetty  
U.S. Army Aviation Applied Technology Directorate  
Ft. Eustis, Virginia 23604

## Abstract

Experimental fatigue tests were performed to determine the surface durability life of a face gear in mesh with a tapered spur involute pinion. Twenty-four sets of gears were tested at three load levels: 7200, 8185, and 9075 lb-in face gear torque, and 2190 to 3280 rpm face gear speed. The gears were carburized and ground, shot-peened and vibro-honed, and made from VIM-VAR Pyrowear 53 steel per AMS 6308. The tests produced 17 gear tooth spalling failures and 7 suspensions. For all the failed sets, spalling occurred on at least one tooth of all the pinions. In some cases, the spalling initiated a crack in the pinion teeth which progressed to tooth fracture. Also, spalling occurred on some face gear teeth. The AGMA endurance allowable stress for a tapered spur involute pinion in mesh with a face gear was determined to be 275 ksi for the material tested. For the application of a tapered spur involute pinion in mesh with a face gear, proper face gear shim controlled the desired gear tooth contact pattern while proper pinion shim was an effective way of adjusting backlash without severely affecting the contact pattern.

## Introduction

Military requirements and commercial economic survivability continuously drive the needs for reduced weight and increased power density for aircraft drive systems. Modern drive system components operate at high speeds, high loads, and high temperatures, and require state-of-the-art in design and materials. A few years ago, the U.S. Army funded a study named the Advanced Rotorcraft Transmission Program (ART I) to investigate improved concepts to reduce helicopter drive system weight and noise, and increase life (ref. 1). From that, the use of face gears in transmissions emerged as a way to achieve these goals.

Results from the original studies showed that a split-torque, face-gear transmission gave a 40% decrease in weight compared to a conventional design for an advanced attack helicopter application (ref. 2). Face gears, however, had no previous application in high-power systems. Much work had to be done

to establish design guidelines. Early analytical work developed face-gear geometry, methods to control the tooth contact, and simulation of meshing and transmission error prediction (ref. 3) as well as tooth generation and methods to define limiting inner and outer radii (ref. 4). Initial experiments demonstrated the feasibility for the use of face gears in helicopter applications but depicted the need for high-accuracy, high-strength, carburized and ground gears (refs. 5 to 7). A DARPA-funded Technology Reinvestment Program (TRP) was established to develop face gear grinding techniques and demonstrate face gears in an actual helicopter gearbox. From this, design guidelines were refined and a grinding methodology using a worm wheel generator was developed (ref. 8). A face gear grinding machine was fabricated, a novel split-torque, face-gear transmission for the U.S. Army AH-64 Apache helicopter application was explored, and load sharing experiments were performed (refs. 9 and 10). The proof-of-concept tests demonstrated effective torque sharing and that face gears yielded good potential for significant weight, cost, and reliability improvements over existing equipment using spiral-bevel gearing.


Further advancements were made in face gear technology in support of the U.S. Army Rotorcraft Drive Systems for the 21st Century (RDS–21) Program performed by Boeing under agreement with the Aviation Applied Technology Directorate of the U.S. Army Aviation and Missile Command. The geometry for tapered pinions and idlers for use in a split-torque, face-gear transmission were analyzed (refs. 11 and 12). Detailed face gear tooth contact and bending stress predictions based on finite element and contact solvers were developed (ref. 13). Further analytical studies investigating torque sharing among multiple pinions and idlers, as well as the effect of tail-rotor power taken from an idler, were performed (ref. 14). In addition to studies for the AH-64, face gear applications for the U.S. Army UH-60 Blackhawk helicopter were investigated (ref. 15).

In addition to the U.S., the interest in face gears grew in popularity abroad. A European program called FACET (“The development of face gears for use in aerospace transmission”) was established amongst the U.K., France, Germany, and Italy

The objective of this study is to determine the surface durability life of a face gear in mesh with a tapered spur involute pinion. Experimental fatigue tests were performed at the Glenn Research Center. The effect of shimming on backlash and contact pattern was investigated. Preliminary tests were performed to evaluate a few pinion and face gear design parameters. Last, endurance tests were performed on twenty-four sets of gears at three loads levels.

## Test Facility

NASA/TM—2007-214970



## Test Gears

2

The face width of the spur pinions was 0.8 in, significantly greater than the face gear to allow for backlash adjustment and optimization of tooth contact. The shaft angle was 90° to accommodate the facility. The pinions were slightly tapered, similar to the TRP design and current AH-64 replacement design, which allows the independent setting of backlash for the multiple pinions and idlers in the split-torque transmission application (ref. 9).

TABLE I.—TEST GEAR DESIGN DATA.

AGMA quality.....	12
Number of teeth; pinion, gear.....	19, 73
Diametral pitch.....	10.6
Pressure angle (deg) .....	27.5
Shaft angle (deg) .....	90
Face width (in); pinion, gear.....	0.8, 0.6
Hardness (Rc); case, core .....	62, 38
RMS surface finish.....	16
Material .....	X53 steel

The pinions and face gears were made from carburized and ground vacuum induction melting-vacuum arc remelting (VIM-VAR) Pyrowear 53 steel per AMS 6308 using standard aerospace practices. At 6000 lb-in face gear torque, the calculated AGMA contact stress index was 250 ksi and the calculated AGMA bending stress index was 72 ksi using approximate spur gear calculations per AGMA (ref. 25).

### Test Gear Installation Procedures

Previous studies showed that proper pinion and face gear installation is a criteria for successful operation (ref. 7). Both pinion and face gear adjustments were made (fig. 3).

Figure 4 shows the effect of face gear adjustments on contact pattern and backlash while keeping a constant pinion position. It is clear that the face gear adjustment had a significant effect on both pattern and backlash. Moving the face gear out of mesh increased backlash and moved the contact pattern from heel to toe. On the other hand, moving the face gear into mesh decreased backlash and moved the contact pattern from toe to heel. Figure 5 shows the effect of pinion adjustments on contact pattern and backlash while keeping a constant face gear position. Moving the pinion into mesh decreased backlash, but had a relatively small effect on the face gear tooth contact pattern for the range of adjustments used. Moving the pinion out of mesh increased backlash, and also had a relatively small effect on the face gear tooth contact pattern. As expected, the contact pattern on the pinion tooth moved from heel to toe as the pinion was moved out of mesh (backlash increased), and from toe to heel as the pinion was moved into mesh (backlash decreased). However, since the pinion tooth width was wider than the face gear tooth width, the patterns still remained on the tooth. Thus, adjusting the pinion position was an effective way of adjusting backlash without severely affecting the contact pattern.

The installation procedure for the gears tested was then defined as follows. First, the test-side pinion and face gear were installed in the facility (with no cross shaft connected to the

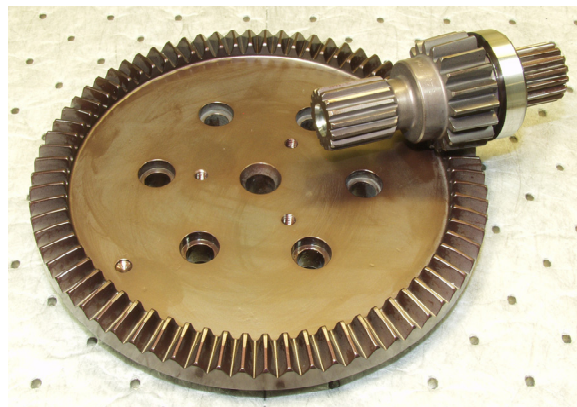


Fig. 2. Test gears.

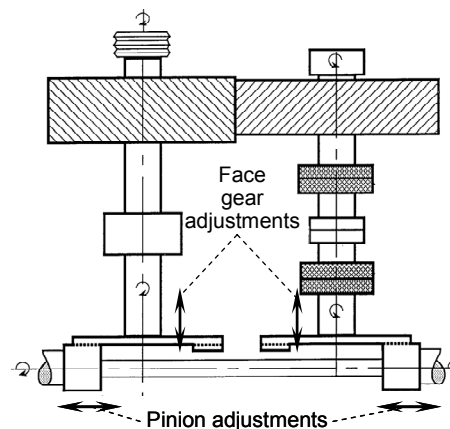


Fig 3. Pinion and face gear shim adjustments.



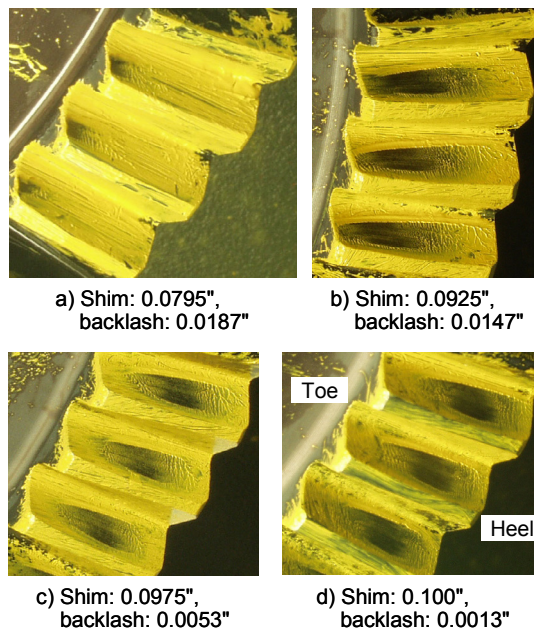


Fig 4. Effect of face gear shim on contact pattern and backlash (all photos shown are face gear patterns).

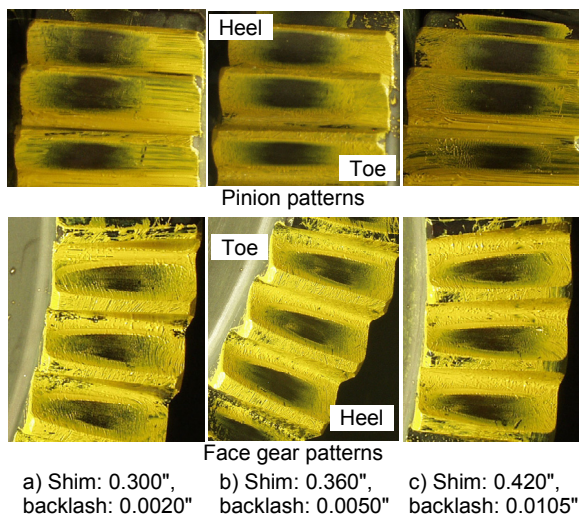

**Fig 5.** Effect of pinion shim on contact pattern and backlash.

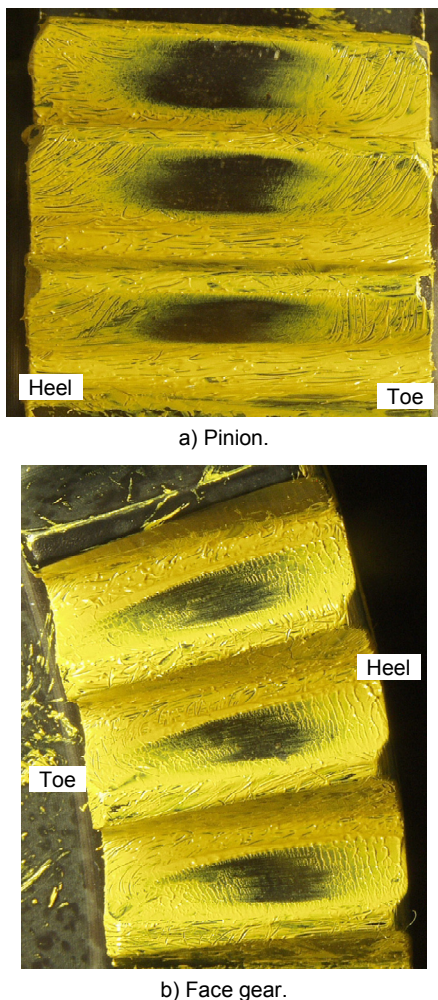


**Fig 6.** Typical contact pattern check, hand resistance.

pinion). Backlash measurements and no-load contact pattern checks were taken for the mesh as described above. A contact pattern biased slightly toward the heel on the face gear and a backlash of 0.006 to 0.010-in was required for this trial. The slight bias of pattern was required since the pattern shifted slightly toward the toe when full load was applied. If necessary, the face gear shim was first adjusted to achieve the proper contact pattern, and then the pinion shim was adjusted to achieve the proper backlash. This process was then repeated for the slave-side pinion/face-gear mesh. Figure 6 shows an acceptable no-load contact pattern. After proper shimming was achieved, the cross shaft was installed. Marking compound was then re-applied to all the pinions and gears and a loaded static roll test was performed. This was done by applying a moderate torque in the loop (through the load piston), manually rotating the complete assembly, and photographing the resulting contact patterns. Figure 7 shows a typical example of a tooth contact pattern check for a loaded static roll test. The objective of this procedure was to ensure that proper backlash and proper shimming was used, edge loading was prevented, and the contact pattern on the face-gear tooth was evenly spread under load.


## Test Procedure

The test procedure to evaluate the fatigue life of face gears was as follows. First, the selected test gears were installed with the proper shims as described above. Backlash measurements as well as un-loaded and loaded contact patterns were documented. After acceptable patterns and backlash, the gears were then run through a break-in procedure. This was a short 70-min run consisting of a gradual increase in speed and torque. The applied torque was obtained using only the load piston. After completion of the break-in run, the gears were inspected. The pre-load coupling was then adjusted to produce a face-gear torque somewhere between 3000 to 5000 lb-in. The gears were then run at required speed and torque for the specific test (torque adjusted using load piston). Facility parameters as well as high-frequency vibration monitoring with gear fault detection software and oil-debris monitoring were collected. During the tests, the gears were inspected at routine intervals (5 to 10 million face gear cycles). The gears were run until a surface durability failure occurred or a suspension was defined. A surface durability failure was defined as macro-pitting or spalling of at least 0.1-in continuous length along the contact area on any tooth of a tested pinion or face gear. Once completed, the gears were removed from the facility, cleaned, and photographed for documentation purposes.

An initial series of tests was done to evaluate various pinion and face gear tooth profiles. The concern was to avoid hard lines on the tooth surfaces. Hard lines are concentrated wear lines that are caused either at the beginning, end, or edge of contact and occur at high loads. Hard lines could cause premature pitting at the region of high contact stress and bias test results. High loads were required for the tests in order to obtain fatigue lives in a reasonable amount of time. Proper adjustments were made

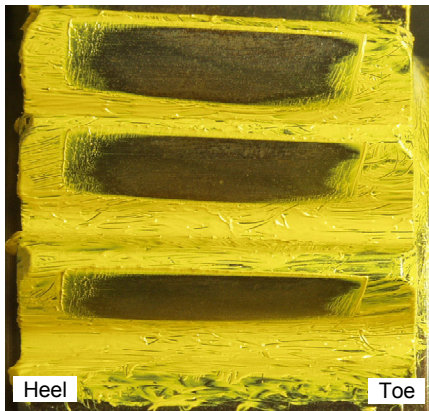

a) Pinion.

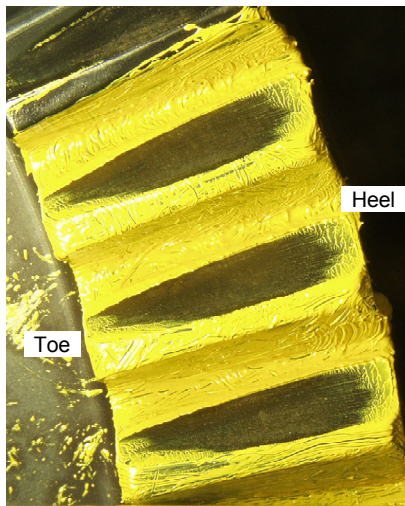

b) Face gear.

**Fig 7.** Typical loaded contact pattern check, ~4400 lb-in gear torque.

to minimize edge contact. In addition, the face gears had slight crowning in the longitudinal direction of the tooth based on methods by Litvin (ref. 8). This also minimized edge contact. Thus, the concern of tip and root contact was studied. Various pinion tip and root relief profiles were tested (table II). In addition, face gear tooth tip designs with increased edge break were investigated (table III). These gears were finished using a rolled-brushing process. Six tests were performed at 6000 lb-in face gear torque and face gear speeds from 3280 to 4700 rpm, depending on the vibration levels of the test.

**TABLE II.—PINION DESIGN VARIATION PARAMETERS.**

Pinion design	Root relief (in)	Tip relief (in)	Number tested
Mod1	0.0004	0.0002	2
Mod2	0.0007	0.0005	2
Mod3	0.0010	0.0002	4
Mod4	0.0014	0.0002	5
Mod5	0.0012	0.0002	1

**TABLE III.—FACE GEAR DESIGN VARIATION PARAMETERS.**

Face Gear Design	Tip radius (in)	Number tested
Original	0.010	6
Rolled-tips	0.010	6
Increased-rolled-tips	0.020	2

After completion of the tooth profile evaluations, the Mod3 pinion design and Rolled-tips face gear design (tables II and III) were chosen for the endurance tests. In addition, the face gears were shot-peened and vibro-honed to match conditions proposed for the AH-64 replacement design. Twenty-four sets of this design were fabricated. Tests were performed at three load levels: 7200 lb-in face gear torque (275 ksi calculated AGMA contact stress), 8185 lb-in face gear torque (292 ksi contact stress), and 9075 lb-in face gear torque (307 ksi contact stress). Test speeds were 2190 to 3280 rpm face gear speed, depending on the vibration levels of the test. Note that for these test conditions, it was estimated that the test sets operated in the mixed elasto-hydrodynamic/boundary lubrication regime based on calculate oil film thicknesses.

## Results and Discussion

Twenty-four sets of gears were tested as part of the endurance tests using the Mod3 pinion design and Rolled-tips face gear design. Twelve sets were tested on the left (test) side and twelve were tested on the right (slave) side. Tests were performed at three load levels: 7200 lb-in face gear torque (275 ksi calculated AGMA contact stress), 8185 lb-in face gear torque (292 ksi contact stress), and 9075 lb-in face gear torque (307 ksi contact stress). Test speeds were 2190 to 3280 rpm face gear speed, depending on the vibration levels of the test. Of the twenty-four sets tested, 17 resulted in spalling failures and 7 were suspended with no spalling. The number of cycles tested per set ranged from 32.7 to 590.9 million pinion cycles. For all the failed sets, spalling occurred on at least one tooth for all the pinions. In some cases, the spalling initiated a crack in the pinion teeth which progressed to tooth fracture. In some cases, spalling occurred on face gear teeth, although this was not the norm.

Figure 8 gives the results of all the twenty-four sets on a S/N (stress/cycle) plot. The vertical axis is calculated AGMA contact stress,  $S_c$ . The horizontal axis is pinion cycles. Again, all failures plotted are from spalling. Also plotted in figure 8 is a regression curve fit of the test data using a two-parameter power function (dotted line). The curve fit neglects suspended items. The result of the regression fit relating contact stress,  $S_c$ , to number of cycles,  $N$ , is

$$S_c = 422.5 N^{-0.021} \quad (1)$$

Lives using AGMA guidelines (ref. 25) for spur and helical gears are also plotted in figure 8. These lives were determined

from the AGMA stress cycle factor,  $Z_n$ , as a function of stress cycles,  $N$ , where

$$Z_n = \begin{cases} 2.466 N^{-0.056} & \text{for } N < 10^7 \text{ cycles} \\ 1.4488 N^{-0.023} & \text{for } N > 10^7 \text{ cycles} \end{cases} \quad (2)$$

and

$$S_c = Z_n S_{ac} \quad (3)$$

where  $S_{ac}$  is the AGMA allowable contact stress. Here, the stress cycle factor,  $Z_n$ , is equal to one at  $N=10,000,000$  cycles. The allowable contact stress was set to equal to  $S_{ac}=275$  ksi, corresponding to a Grade 3 material in the AGMA guidelines (ref. 25) since the test gears were VIM-VAR steel. Using eqs. (2) and (3), relating contact stress,  $S_c$ , to number of cycles,  $N$ , gives

$$S_c = \begin{cases} 678.2 N^{-0.056} & \text{for } N < 10^7 \text{ cycles} \\ 398.4 N^{-0.023} & \text{for } N > 10^7 \text{ cycles} \end{cases} \quad (4)$$

which is plotted in figure 8. As can be seen from eqs. (1) and (4), the slope of the regression fit on the test data matches very closely to that of the AGMA for  $N>10^7$  cycles.

Figure 9 is a Weibull plot of the endurance data points at the 275-ksi contact stress level. The data for the plot was created using methods of Johnson (ref. 26). The procedure plots the medium rank of the data point as a function of number of cycles. The medium rank is also adjusted for suspensions. The data is plotted on special Weibull logarithmic axes. Also included in the plot are 90% confidence bands. Specific lives from the analysis are tabulated in table IV. Shown are the  $L_1$  life (1% probability of failure),  $L_{10}$  life (10% probability of failure),  $L_{50}$  life (50% probability of failure), and mean life as well as upper and lower 90% confidence band limits. For tests at 275 ksi contact stress, the Weibull slope was 1.67 and the failure index was 7 out of 12 (7 failures out of 12 total sets). Figure 10 is a Weibull plot of the endurance data points at the 292-ksi contact stress level. Here, the

Weibull slope was 1.54 and the failure index was 4 out of 6. Figure 11 is a Weibull plot of the endurance data points at the 307-ksi contact stress level. Here, the Weibull slope was 2.23 and the failure index was 6 out of 6. Specific lives for these test conditions are also tabulated in table IV.

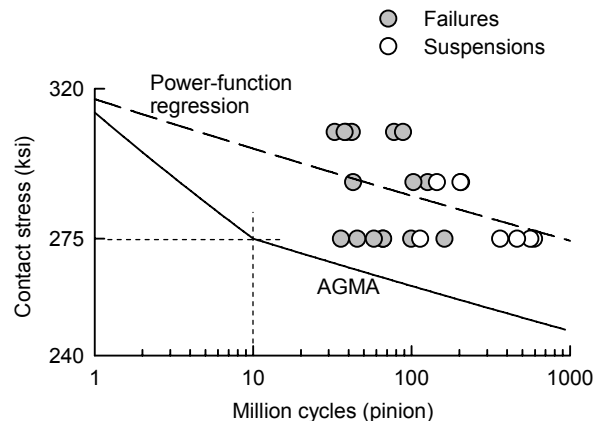


Fig 8. S/N (stress/cycle) plot results of face gear endurance tests.


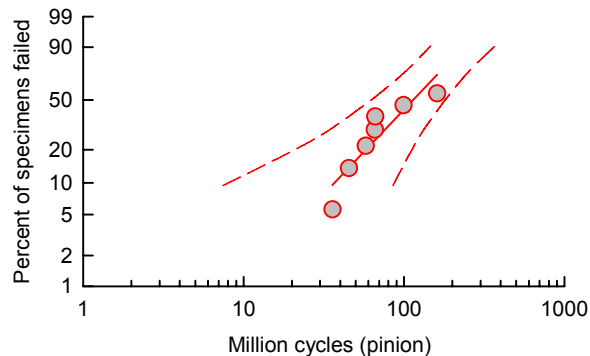



Fig 9. Weibull plot with 90% confidence bands, endurance runs data at 275 ksi contact stress.

TABLE IV.—SUMMARY OF FATIGUE LIVES FROM WEIBULL ANALYSIS, ENDURANCE TEST RESULTS

			Contact stress (ksi)		
			275	292	307
Gear set life, M Cycles (pinion)	L <sub>1</sub>	Lower 90% Confidence Limit	---	---	---
		Experimental	9.0	9.4	7.8
		Upper 90% Confidence Limit	47.5	72.1	27.6
	L <sub>10</sub>	Lower 90% Confidence Limit	8.1	4.3	6.4
		Experimental	36.8	43.2	22.2
		Upper 90% Confidence Limit	86.6	132.1	43.5
	L <sub>50</sub>	Lower 90% Confidence Limit	62.4	61.2	31.8
		Experimental	114.0	147.2	51.8
		Upper 90% Confidence Limit	181.0	272.6	75.1
	L <sub>mean</sub>	Lower 90% Confidence Limit	71.9	74.2	33.7
		Experimental	126.9	168.3	54.1
		Upper 90% Confidence Limit	198.0	302.8	77.7
Weibull slope		1.67	1.54	2.23	
Failure index		7 out of 12	4 out of 6	6 out of 6	

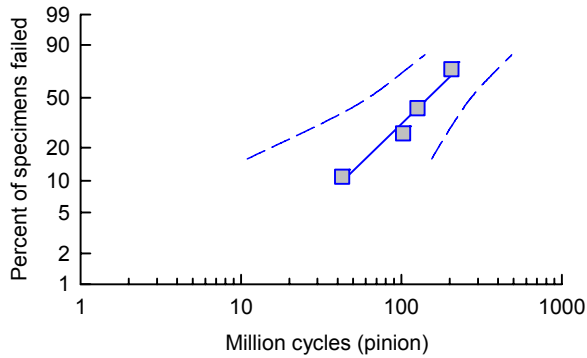


**Fig 10.** Weibull plot with 90% confidence bands, endurance runs data at 292 ksi contact stress.

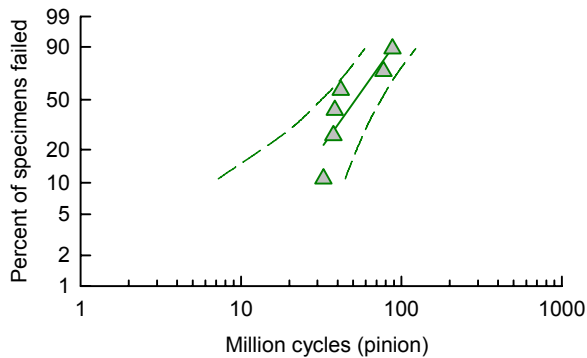


**Fig 11.** Weibull plot with 90% confidence bands, endurance runs data at 307 ksi contact stress.

Figure 12 combines all the data from the 275, 292, and 307-ksi contact stress levels (figs. 9 to 11) into a single plot. As seen from this figure and with table IV as well, the resulting lives at 275 ksi were less than that at 292 ksi. This inconsistency was due to two factors. The first was caused by a couple of relatively low-life outcasts at the 275-ksi stress level. Second was the number of failure points. Even though 24 sets were tested and 17 failures were produced, more data was needed to produce statistically significant results.

This is also evident in table V where the significance of the resulting lives at the 292-ksi and 307-ksi stress levels are compared to that at 275 ksi. This table was created using the methods of Johnson (ref. 26) in which the confidence that the lives of a tested population are greater (or less) than those of another tested population is explored. This confidence is based on the sample sizes (number of failures for both populations) and life ratios of the populations, either at the  $L_{10}$  life or mean life level. From table V, the confidence of the  $L_{10}$  life at 307 ksi stress relative to 275 ksi is 70%. This means that 70 times out of 100, the  $L_{10}$  population life at 307 ksi is less than that at 275 ksi. The confidence of the  $L_{10}$  life at 292 ksi stress relative to 275 ksi is only 54%. Confidence numbers in the 70 to 80% range are rather marginal in significance. Numbers in the 50 to 60% range indicate no significant difference. The only conclusion that can be drawn with high confidence is that the mean life at 307 ksi is statistically less than that at 275 ksi (confidence >99%).

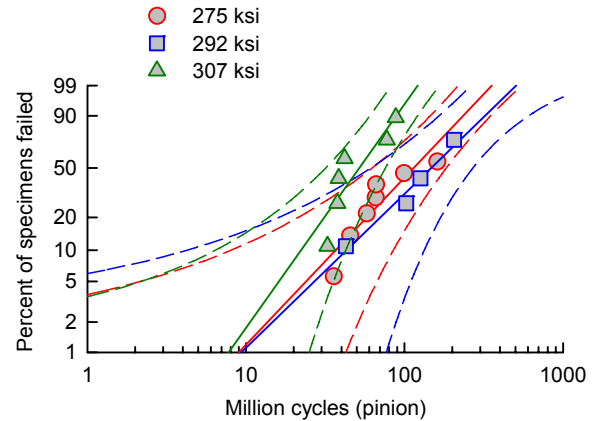

**Fig 12.** Weibull plots, endurance runs data, all stress conditions.

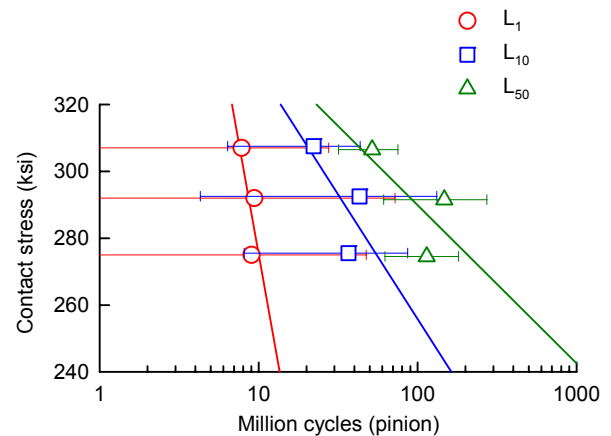

**Fig 13.** S/N (stress/cycle) plot results of face gear endurance tests at the 99% ( $L_1$ ), 90% ( $L_{10}$ ), and 50% ( $L_{50}$ ) reliability levels.

TABLE V.—SIGNIFICANCE OF FATIGUE LIVES  
RELATIVE TO THOSE AT 275 ksi CONTACT STRESS

	Contact stress (ksi)	
	292	307
$L_{10}$	54%	70%
$L_{mean}$	79%	>99%

The  $L_1$ ,  $L_{10}$ , and  $L_{50}$  lives from the Weibull analysis for the various stress levels are plotted in an S/N curve in figure 13 along with linear curve fits. The purpose was to define the AGMA allowable endurance limit from the test data. AGMA uses the  $L_1$  life in its calculation. That is, the endurance allowable is defined as the load that results in 10 million cycles life for a reliability of fewer than one in 100 failures. From figure 13, the curve fit at the  $L_1$  life level is:

$$S_c = 2146.5 - 267.32 \log(N) \quad (5)$$

From eq. (5), for  $N=10,000,000$  cycles,  $S_{ac}=S_c=275$  ksi. Thus, the AGMA endurance limit from the test data was the same as that for a Grade 3 material as recommended in the AGMA guidelines (ref. 25). The test results support use of the AGMA spur-helical gear method for estimating the pitting resistance of face gear sets.

## Conclusions

Experimental fatigue tests were performed to determine the surface durability life of a face gear in mesh with a tapered spur involute pinion. The tests were performed at the Glenn Research Center in the Glenn spiral-bevel-gear/face-gear test facility. The effect of shimming on backlash and contact pattern was investigated. Preliminary tests were performed to evaluate a few pinion and face gear design parameters. Lastly, endurance tests were performed on twenty-four sets of gears at three loads levels. The following results were obtained:

(1) The AGMA endurance allowable stress for a tapered spur involute pinion in mesh with a face gear was determined to be 275 ksi for carburized and ground, shot-peened and vibro-honed, vacuum induction melting-vacuum arc remelting (VIM-VAR) Pyrowear 53 steel per AMS 6308. The tests produced 17 gear tooth spalling failures and 7 suspensions. For all the failed sets, spalling occurred on at least one tooth of all the pinions. In some cases, the spalling initiated a crack in the pinion teeth which progressed to tooth fracture. Also, spalling occurred on some face gear teeth, although this was not the norm.

(2) Even with 17 failure points, the statistical significance of the endurance tests results was marginal when tested at three load levels.

(3) For the application of a tapered spur involute pinion in mesh with a face gear, proper face gear shim controlled the desired gear tooth contact pattern while proper pinion shim was an effective way of adjusting backlash without severely affecting the contact pattern.

## References

1. Bill, R.C., "Advanced Rotorcraft Transmission Program," Proceedings of the 46th American Helicopter Society Annual Forum, Washington, DC, May 21, 1990.
2. Heath, G.F., and Bossler, R.B., "Advanced Rotorcraft Transmission (ART) Program - Final Report," NASA Contractor Report CR-191057, Army Research Laboratory Contractor Report ARL-CR-14, McDonnell Douglas Helicopter Company, Contract NAS3-25454, Jan. 1993.
3. Litvin, F.L., Zhang, Y., Wang, J.-C., Bossler, R.B., and Chen, Y.-J.D., "Design and Geometry of Face-Gear Drives," ASME Journal of Mechanical Design, vol. 114, no. 4, Dec. 1992, pp. 642-647.
4. Litvin, F.L., Wang, J.-C., Bossler, R.B., Chen, Y.-J.D., Heath, G.F., and Lewicki, D.G., "Application of Face-Gear Drives in Helicopter Transmission," ASME Journal of Mechanical Design, vol. 116, no. 3, Sep. 1994, pp. 672-676.
5. Handschuh, R.F., Lewicki, D.G., and Bossler, R.B., "Experimental Testing of Prototype Face Gears for Helicopter Transmissions," Journal of Aerospace Engineering, Proceedings of the Institute of Mechanical Engineers, vol. 208, no. G2, Oct. 1994, pp. 129-135.
6. Handschuh, R.F., Lewicki, D.G., Heath, G.F., and Bossler, R.B., "Experimental Evaluation of Face Gears for Aerospace Drive System Applications," Proceedings of the ASME 7th International Power Transmission and Gearing Conference, San Diego, CA, Oct. 6-9, 1996, pp. 581-588.
7. Lewicki, D.G., Handschuh, R.F., Heath, G.F., and Sheth, V., "Evaluation of Carburized and Ground Face Gears," Journal of the American Helicopter Society, vol. 45, no. 2, Apr. 2000, pp. 118-124.
8. Litvin, F.L., Egelja, A., Tan, J., Chen, Y.-J.D., and Heath, G.F., "Handbook on Face Gear Drives With a Spur Involute Pinion," NASA Contractor Report NASA/CR-2000-209909, Army Research Laboratory Contractor Report ARL-CR-447, The Boeing Company, Cooperative Agreement NCC3-356, Mar. 2000.
9. Heath, G.F., Filler, R.R., and Tan, J., "Development of Face Gear Technology for Industrial and Aerospace Power Transmission," NASA Contractor Report NASA/CR-2002-211320, Army Research Laboratory Contractor Report ARL-CR-0485, The Boeing Company, Cooperative Agreement NCC3-356, May 2002.
10. Filler, R.R., Heath, G.F., Slaughter, S.C., and Lewicki, D.G., "Torque Splitting By a Concentric Face Gear Transmission," Proceedings of the 58th American Helicopter Society Annual Forum, Montreal, Quebec, Canada, Jun. 11-13, 2002.
11. Tan, J., "Face Gearing With A Conical Involute Pinion Part 1. The Conical Involute Gear -- Definition, Geometry And Generation," Proceedings of the ASME Mechanisms and Robotics Conference, Montreal, Canada, Sep. 29, 2002.
12. Tan, J., "Face Gearing With a Conical Involute Pinion: Part 2 (The Face Gear: Meshing With the Pinion, Tooth Geometry and Generation)," Proceedings of the ASME 9th International Power Transmission and Gearing Conference / AGMA Fall Technical Conference, Chicago, IL, Sep. 3-5, 2003.
13. Smith, K.B., and Filler, R.R., "Face Gear Finite Element Stress Analysis Tool Development," Proceedings of the 60th American Helicopter Society Annual Forum, Baltimore, MD, Jun. 7-10, 2004.
14. Chun, H.-W., Filler, R.R., and Tan, J., "Analytical Determination of Load Distribution in a Statically Indeterminate Face Gear Transmission," Proceedings of the 62nd American Helicopter Society Annual Forum, Phoenix, AZ, May 9-11, 2006.
15. Binney, D.A., Vinayak, H., Gmirya, Y., Zunski, L.M., Houser, D.R., and Ames, E.C., "Face Gear Transmission Development Program at Sikorsky Aircraft," Proceedings of the ASME 9th International Power Transmission and Gearing Conference / AGMA Fall Technical Conference, Chicago, IL, Sep. 3-5, 2003.
16. Caruso, A., and Gorla, C., "FACET" - Face gears in aerospace transmissions," Proceedings of the 25th European Rotorcraft Forum, vol. 2, Rome, Italy, Sep. 14-16, 1999.
17. Jacquin, C.-Y., Guingand, M., Vaujany, J.-P.D., and Play, D., "Contact Analysis of Helical Face Gears," Proceedings of the ASME 8th International Power Transmission and Gearing Conference, Baltimore, MD, Sep. 10-13, 2000.
18. Guingand, M., Vaujany, J.-P.d., and Icard, Y., "Analysis and Optimization of the Loaded Meshing of Face Gear," Proceedings of the ASME 9th International Power Transmission and Gearing Conference / AGMA Fall Technical Conference, Chicago, IL, Sep. 3-5, 2003.

19. Guingand, M., Vaujany, J.-P., and Jacquin, C.-Y., "Quasi-static analysis of a face gear under torque," *Computer Methods in Applied Mechanics and Engineering*, vol. 194, no. 39–41, Oct. 2005, pp. 4301–4318.
20. Sato, Y., and Akahori, H., "Evaluation of Face Gear for Rotorcraft Application," *Proceedings of Heli Japan 2002*, Tochigi, Japan, Nov. 11–13, 2002, pp. 601–608.
21. Moriwaki, I., Ogaya, S., and Watanabe, K., "Stress Analysis of Face Gear Tooth Subject to Distributed Load Using Global Local Finite Element Method (GLFEM)," *Proceedings of the ASME 9th International Power Transmission and Gearing Conference/AGMA Fall Technical Conference*, Chicago, IL, Sep. 3–5, 2003.
22. Weck, M., Hurasky-Schonwerth, O., and Yakaria, H., "Manufacturing Simulation for Generation Grinding of Face Gears," *Proceedings of the International Conference on Gears*, vol. I, Munich, Germany, Mar. 13–15, 2002, pp. 379–394.
23. Barone, S., Borgianni, L., and Forte, P., "Evaluation of the Effect of Misalignment and Profile Modification in Face Gear Drive by a Finite Element Meshing Simulation," *Proceedings of the ASME 9th International Power Transmission and Gearing Conference / AGMA Fall Technical Conference*, Chicago, IL, Sep. 3–5, 2003.
24. Zanzi, C., and Pedrero, J.I., "Application of modified geometry of face gear drive," *Computer Methods in Applied Mechanics and Engineering*, vol. 194, no. 27–29, Jul. 22, 2005, pp. 3047–3066.
25. ANSI/AGMA 2001–C95, "Fundamental Rating Factors and Calculation Methods for Involute Spur and Helical Gear Teeth," The American Gear Manufacturers Association, 1995.
26. Johnson, L., *The Statistical Treatment of Fatigue Experiments*, Elsevier, New York, 1964.

REPORT DOCUMENTATION PAGE				Form Approved OMB No. 0704-0188	
<p>The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.</p> <p>PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.</p>					
1. REPORT DATE (DD-MM-YYYY) 01-09-2007		2. REPORT TYPE Technical Memorandum		3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE RDS-21 Face-Gear Surface Durability Tests				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) Lewicki, David, G.; Heath, Gregory, F.; Filler, Robert, R.; Slaughter, Stephen, C.; Fetty, Jason				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER WBS 877868.02.07.03.01.01	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration John H. Glenn Research Center at Lewis Field Cleveland, Ohio 44135-3191				8. PERFORMING ORGANIZATION REPORT NUMBER E-16123	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, DC 20546-0001 and U.S. Army Research Laboratory Adelphi, Maryland 20783-1145				10. SPONSORING/MONITORS ACRONYM(S) NASA, ARL	
				11. SPONSORING/MONITORING REPORT NUMBER NASA/TM-2007-214970; ARL-TR-4089	
12. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified-Unlimited Subject Category: 37 Available electronically at <a href="http://gltrs.grc.nasa.gov">http://gltrs.grc.nasa.gov</a> This publication is available from the NASA Center for AeroSpace Information, 301-621-0390					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT Experimental fatigue tests were performed to determine the surface durability life of a face gear in mesh with a tapered spur involute pinion. Twenty-four sets of gears were tested at three load levels: 7200, 8185, and 9075 lb-in face gear torque, and 2190 to 3280 rpm face gear speed. The gears were carburized and ground, shot-peened and vibro-honed, and made from VIM-VAR Pyrowear 53 steel per AMS 6308. The tests produced 17 gear tooth spalling failures and 7 suspensions. For all the failed sets, spalling occurred on at least one tooth of all the pinions. In some cases, the spalling initiated a crack in the pinion teeth which progressed to tooth fracture. Also, spalling occurred on some face gear teeth. The AGMA endurance allowable stress for a tapered spur involute pinion in mesh with a face gear was determined to be 275 ksi for the material tested. For the application of a tapered spur involute pinion in mesh with a face gear, proper face gear shim controlled the desired gear tooth contact pattern while proper pinion shim was an effective way of adjusting backlash without severely affecting the contact pattern.					
15. SUBJECT TERMS Gears; Fatigue life; Weibull density functions					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES 15	19a. NAME OF RESPONSIBLE PERSON STI Help Desk (email: <a href="mailto:help@sti.nasa.gov">help@sti.nasa.gov</a> )
a. REPORT U	b. ABSTRACT U	c. THIS PAGE U			19b. TELEPHONE NUMBER (include area code) 301-621-0390



